

Spin dynamics of the ferromagnetic superconductor UGe₂

S. Raymond^{1,2} and A. Huxley¹

¹CEA-Grenoble, DSM / DRFMC / SPSMS, 38054 Grenoble, France

²Institut Laue Langevin, 38042 Grenoble, France

Inelastic neutron scattering was used to study the low energy magnetic excitations of the ferromagnetic superconductor UGe₂. The ferromagnetic fluctuations are of Ising nature with a non-conserved magnetization and have an intermediate behavior between localized and itinerant magnetism.

PACS numbers: 74.70.Tx, 75.40.Gb, 78.70.Nx

Superconductivity occurring close to an antiferromagnetic quantum critical point is now well documented. In the magnetically mediated model for superconductivity, the formation of Cooper pairs is also expected close to a low temperature ferromagnetic transition. But it is only very recently that the first experimental evidence for the coexistence of ferromagnetism and bulk superconductivity was found in UGe₂ under pressure [1, 2]. At 12 kbar, the superconducting transition temperature is maximum ($T_c \approx 0.7$ K) while the ferromagnetism remains strong with $T_{Curie} \approx 30$ K and a magnetic moment of $1 \mu_B$. Given the large internal field, triplet superconductivity is likely. In order to get a microscopic insight into this new physics, we have performed inelastic neutron scattering (INS) experiments on a single crystal of UGe₂ using the cold three axis spectrometer IN14 at the Institut Laue Langevin, France. UGe₂ crystallizes in the Cmmm space group with $a=3.99$ Å, $b=15.04$ Å and $c=4.09$ Å.

Quasielastic scattering corresponding to critical and paramagnetic scattering was measured in the range 20-70 K. Typical spectra obtained at $T=65$ K are shown in Fig.1 for $\mathbf{Q}=(0, 0, 1.02)$ and $\mathbf{Q}=(0, 0, 1.08)$ (Here, $\mathbf{Q}=\tau+(q_h, q_k, q_l)$, where τ is a Bragg peak and each coordinate expressed in reciprocal lattice units). Most data were taken along the c-axis and in the following, we write $q = q_l$. The data were fitted using the double Lorentzian form :

$$\chi''(q, \omega) = \frac{\chi_0}{1 + (q/\kappa)^2} \frac{\omega \Gamma_q}{\omega^2 + \Gamma_q^2} \quad (1)$$

with χ_0 the bulk susceptibility, κ the inverse correlation length and Γ_q the relaxation rate. The first fraction in (1) is the q -dependent susceptibility χ_q . Details of the data analysis and results are given elsewhere [3]. For each temperature, Γ_q is directly obtained from constant q scans ; κ and χ_0 are deduced by a fit of χ_q (obtained by integrating over energy $\chi''(q, \omega)/\omega$). Here, we emphasize the main points [3]. i) Only longitudinal fluctuations were observed confirming the Ising nature of the system. ii) These fluctuations are observed both above and below T_{Curie} and no new Goldstone modes are observed below T_{Curie} . iii) the product $\Gamma_q \chi_q$ is independent of temperature above T_{Curie} but drops when T decreases below T_{Curie} . iv) Except at T_{Curie} , it is found that the magnetization is not conserved, in other words the relaxation

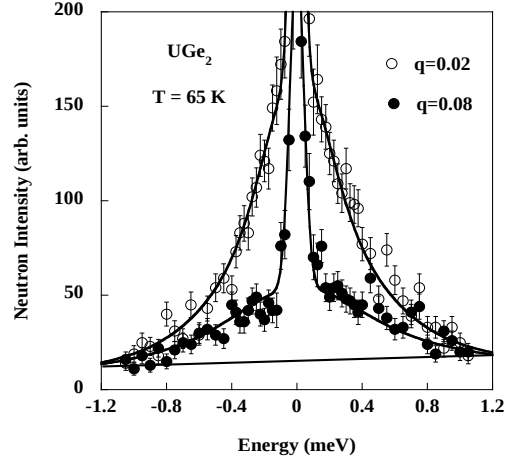


FIG. 1: Energy response of the magnetic signal for $\mathbf{Q}=(0,0,1.02)$ and $\mathbf{Q}=(0,0,1.08)$ at $T=65$ K. Lines correspond to fit to Lorentzian functions as described in the text. The lower solid line denotes the background estimated from measurements performed at 1.5 K. The narrow central peak corresponds to incoherent background.

rate Γ_q is finite in the limit $q \approx 0$. In this short paper, we focus on the relationship above T_{Curie} between the relaxation rate and the inverse correlation length and compare this with the predictions for dynamical scaling theory for kinetic Ising model with a non-conserved magnetization [4]. In [3], it was shown that $\chi_0 \kappa^2$ is independent of temperature. Above T_{Curie} , $\chi_0 \Gamma_0$ is also temperature independent (at $q=0$ as for any q value). We then have $\Gamma_0 = a \kappa^2$. Such a relation is shown in Fig.2 where T is an implicit parameter. The best fit is obtained with $a=50(1) \text{ meV(r.l.u.)}^{-2}$. Such a relation is also found for a non-conserved Ising model [4] and implies that the dynamical exponent z equals two in UGe₂ ($\Gamma_0 = a \kappa^z$). The $q \neq 0$ generalization of such a law is the scaling form $\Gamma_q = A q^z f(\kappa/q)$. The result of such an analysis based on the collapse onto a single curve of data obtained at 55, 60, 65 and 70 K is shown in Fig.3 with $f(x) = 1 + x^2$, $z=2$ and $A=49(1) \text{ meV(r.l.u.)}^{-2}$. There is a very good agreement between the determination of a and A (a is determined from a subset of data with $q=0$). Such plots have also been made for metallic Heisenberg ferromagnets, but with $z=2.5$ as expected from dynamical scaling

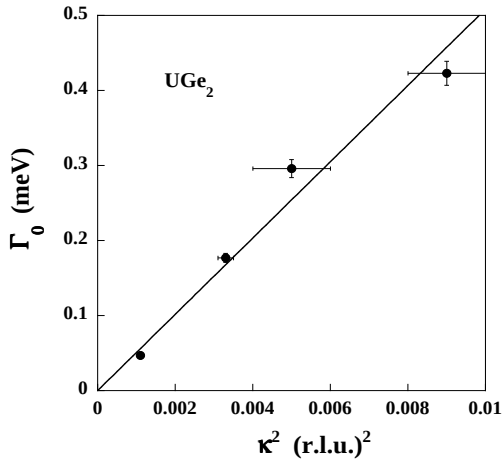


FIG. 2: Γ_q at $q=0$ as a function of κ^2 , where temperature is an implicit parameter. The line is a linear fit to the data.

theory for that case [4]. The same scaling function f was applied to MnSi [5], CoS₂[6] and Ni₃Al[7]. In these compounds it was argued that the form of f is related to the itinerant character of the system and contrasts with the form expected for localized systems where f is experimentally found to be close to that calculated by Résibois-Piette [8]. For UGe₂, the z and f used to describe the data simply correspond to $\Gamma_q = A(\kappa^2 + q^2)$, with all the temperature dependence included in κ .

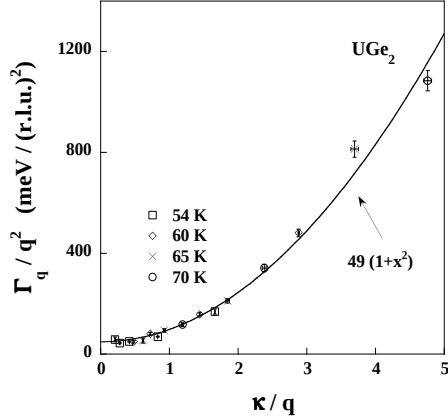


FIG. 3: Γ_q/q^2 as a function of κ/q . The line is a fit to the data using dynamical scaling theory as explained in the text.

In the study of the Heisenberg ferromagnets, focus was also given to the quantity κ_0 defined by the temperature variation of the inverse correlation length, $\kappa(T)^2 = \kappa_0^2(T/T_{Curie} - 1)^{2\nu}$ above T_{Curie} . For UGe₂, we found $\nu=0.5$ and $\kappa_0^2 \approx 0.08 \text{ \AA}^{-2}$ [3]. The quantities κ_0 and A characterize the extension of the spin fluctuations in q and ω space respectively. In itinerant systems, the extension is narrow in q space and wide in ω space [9]. To this respect, κ_0^2 is small as in the itinerant system MnSi ($0.035 \text{ \AA}^{-2}$ [5]) while it is generally larger in lo-

calized systems ($0.41 \text{ \AA}^{-2}$ in EuO, $1.1 \text{ \AA}^{-2}$ in Fe). The ratio A/T_{Curie} is also usually used to describe the energy spread of spin fluctuations [6, 9]. For UGe₂, we found $A/T_{Curie} \approx 0.9 \text{ meV/K}$. In fact to compare with Heisenberg systems, A must be re-scaled to A' in order to take into account the difference in z between kinetic Ising and Heisenberg systems (e.g. $A'q_{ZB}^{2.5} = Aq_{ZB}^2$ where q_{ZB} is the zone boundary wave-vector). After such a phenomenological correction, the ratio A'/T_{Curie} for UGe₂ (1.3 meV/K) is about twice the one of EuO (0.77 meV/K) and half the one of MnSi (3.3 meV/K). This intermediate behavior between localized and itinerant magnetism was also pointed out in the study of the temperature variation of the order parameter for several pressures [11].

The spin dynamics of UGe₂ is of fundamental interest for magnetism by itself since there are a few detailed INS studies on Ising ferromagnets [12]. Considering UGe₂ as such a model system above T_{Curie} , the prediction of dynamical critical phenomena for the kinetic Ising model with a non-conserved magnetization are experimentally verified as shown by the scaling of the neutron linewidth implying a dynamical exponent, $z=2$. As concerns superconductivity, microscopic parameters like Γ_q and κ_0 are necessary inputs in the theory of magnetically mediated superconductivity [13]. The Ising fluctuations favor triplet superconductivity together with the rather low value of κ_0 . However the evolution of these parameters as a function of pressure in the range where superconductivity occurs has to be measured.

We acknowledge ILL staff for technical support and discussions concerning optimal use of instrument with A. Stunault.

-
- [1] S.S. Saxena et al., Nature 406 (2000) 587.
 - [2] A. Huxley et al., Phys. Rev. B 63 (2001) 144519.
 - [3] A. Huxley, S. Raymond and E. Ressouche, Phys. Rev. Lett. 91 (2003) 207201.
 - [4] P.C. Hohenberg and B.I. Halperin, Rev. Mod. Phys. 49 (1977) 435.
 - [5] Y. Ishikawa et al., Phys. Rev. B 31 (1985) 5884.
 - [6] H. Hiraka et al., J. Phys. Soc. Japan 66 (1997) 818.
 - [7] F. Semadeni et al., Phys. Rev. B 62 (2000) 1083.
 - [8] P. Résibois and C. Piette, Phys. Rev. Lett. 24 (1970) 514.
 - [9] T. Moriya, Spin fluctuations in itinerant electron magnetism, Springer, Berlin 1985.
 - [10] G. Shirane et al., Phys. Rev. B 31 (1985) 1227.
 - [11] A. Huxley et al., J. Phys. Cond. Matter 15 (2003) S1945.
 - [12] M.F. Collins, Magnetic critical scattering, Oxford University Press, 1989.
 - [13] P. Monthoux and G.G. Lonzarich, Phys. Rev. B 59 (1999) 14598.